
STATE OF ILLINOIS DEPARTMENT OF TRANSPORTATION



Contract No. 62882

★ (105X & 106)WRS-2

Bar splicer assemblies shall be of an approved type and shall develop in tension at least 125 percent of the yield strength of the lapped reinforcement bars.

Splicer rods shall be of minimum 60 ksi yield strength, threaded or coiled full length. All reinforcement bars shall be lapped and tied to the splicer rods or dowel bars. Bar splicer assemblies shall be epoxy coated according to the requirements for reinforcement bars.

Other systems of similar design may be submitted to the Engineer for approval. Approval shall be based on certified test results from an approved testing laboratory that the proposed bar splicer assembly satisfies the following requirements:


Minimum Capacity = $1.25 \times fy \times A_t$

(Lension וון אפקא) Minimum *Pull-out Strength = 0.66 x fy x A₁

Where fy = Yield strength of lapped reinforcement bars in ksi. A_t = Tensile stress area of lapped reinforcement bars.

* = 28 day concrete

BAR SPLICER ASSEMBLIES				
Bar Size to be Spliced	Dowel Bar Lenath	Strength Requirements		
		Min. Capacity kips - tension	Min. Pull-Out Strength kips - tension	
#4	1'-8''	14.7	7.9	
#5	2'-2"	23.0	12.3	
#6	2'-7''	33.1	17.4	
#7	3′-5′′	45.1	23.8	
#8	4'-6''	58.9	31.3	
#9	5′-9′′	75.0	39.6	
#10	7′-3′′	95.0	50.3	
#11	9'-0''	117.4	61.8	

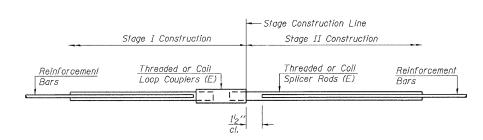


STANDARD

Bar Size	No. Assemblies Required	Location	
#5	148	Culvert Stage Construction Line	



Illinois Firm Registration No.: 1184-001533

BAR SPLICER ASSEMBLY DETAILS IL ROUTE 47 OVER S. BRANCH KISHWAUKEE RIVER F.A.P. 326 - SECT. (105X & 106)WRS-2 MCHENRY COUNTY STATION 25+24.62 STRUCTURE NO. 056-0085

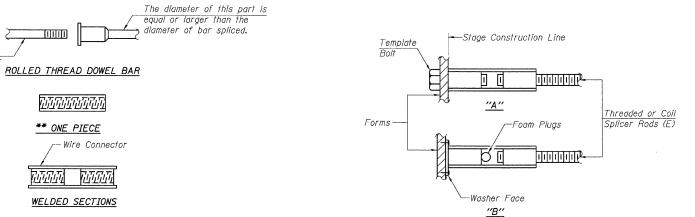


BAR SPLICER ASSEMBLY ALTERNATIVES

**Heavy Hex Nuts conforming to ASTM A 563, Grade C, D or DH may be used.


INSTALLATION AND SETTING METHODS

"A" :Set bar splicer assembly by means of a template bolt. "B" :Set bar splicer assembly by nailing to wood forms or cementing to steel forms.

(E) : Indicates epoxy coating.

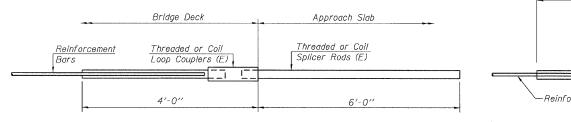

FOR INTEGRAL OR SEMI-INTEGRAL ABUTMENTS




DESIGNED	-
CHECKED	_
DRAWN	- RTT
CHECKED	- DSE
DATE	- Aug. 5, 2009

The diameter of this part

is the same as the diamete

of the bar spliced.

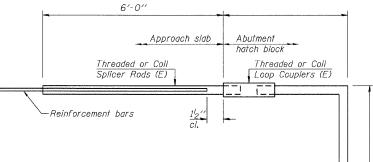

FOR STUB ABUTMENTS

Bar Splicer for #5 bar Min. Capacity = 23.0 kips - tension Min. Pull-out Strength = 12.3 kips - tension No. Required =